



Year: 2018


Natural stone slabs for outside flooring UNI EN 1341:2003
 Internal and external cladding slabs UNI EN 1469:2005
 Natural stone cladding tiles UNI EN 12057:2005
 Internal and external slabs for flooring and stairs UNI EN 12058:2005

GIALLO DORATO

GRASSI PIETRE S.R.L. - Via Madonnetta, 2 - 36024 Nanto (VI)

Characteristics	Declared value (middle value)	Test method
Petrographic description	Biocalcarenite	UNI EN 12407:2007
Reaction to fire	A1 Class	No test (see decicion 96/603/CE and flwing change)
Flexural strength (Th : 40 mm)	5.4 MPa (Th : 40 mm)	UNI EN 12372:2007
Uniaxial compression strength	30,0 MPa (Mid value)	UNI EN 1926:2007
Frost resistance through modification of compression strength	Uniaxial compression strength variation (after 56 cycles -12°C/+20°C): 5,0 MPa (-8%)	UNI EN 12371:2010
Water absorption	9,8 %	UNI EN 13755:2008
Apparent volumic mass	2000 kg/m ³	UNI EN 1936:2007
Abrasion resistance (Method A)	34 mm	UNI EN 14157:2005
Slip resistance (SRV) Finishing: only sawn	85 (wet)	UNI EN 1341:2003
Slip resistance (SRV) Finishing : honed not sealed Finishing: honed sealed * Finishing: Brushed not sealed Finishing: Brushed sealed *	65 (dry) 75 (wet) 69 (dry) 59 (wet) 64 (dry) 68 (wet) 63 (dry) 50 (wet)	UNI EN 14231:2004
Open porosity	17,2%	UNI EN 1936:2007

*: Sealant by FILA, waterbased sealant + 1 hand of wax

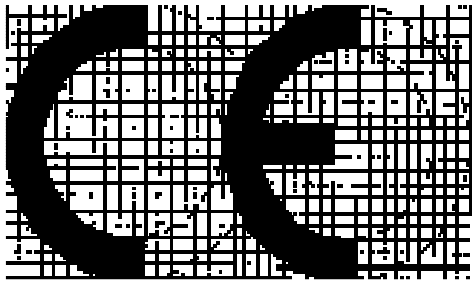

Year: 2018

Natural stone slabs for outside flooring UNI EN 1341:2003
Internal and external cladding slabs UNI EN 1469:2005
Natural stone cladding tiles UNI EN 12057:2005
Internal and external slabs for flooring and stairs UNI EN 12058:2005

GIALLO DORATO

GRASSI PIETRE S.R.L. - Via Madonnetta, 2 - 36024 Nanto (VI)

Charachteristics	Declared value (middle value)	Test method
Breaking load on anchoring holes : pin diam : 6 mm		UNI EN 13364:2003
Thikness: 30 mm (cross cut)	667 N (middle value)	
Thikness: 30 mm (vein cut)	546 N (middle value)	
Thikness: 40 mm (cross cut)	1175 N (middle value)	
Thikness: 40 mm (vein cut)	1088 N (middle value)	
Breaking load on anchoring holes : Kerf 7 mm		UNI EN 13364:2003
Thikness: 30 mm (cross cut)	383 N (middle value)	
Thikness: 30 mm (vein cut)	413 N (middle value)	
Thikness: 40 mm (cross cut)	733 N (middle value)	
Thikness: 40 mm (vein cut)	767 N (middle value)	
Resistance to thermal shock :	- 8,1 %	UNI EN 14066:2013
Flexural strength after thermal shock	Flexural strength variation (after 20 cycles +20°C/+70°C): 4,7 MPa (- 14,8 %)	UNI EN 12372:2007

Tested by: **ECAM - RI.CERT. Spa** – Monte di Malo (VI)